

INNOVATIVE BIOACTIVE RESIN INFILTRANT

Abeer Elsayed ElEmbaby *

ABSTRACT

Integrating nanohydroxyl apatite particles in resin infiltrant is a promising route for treatment of dental caries. This study is aimed to assess the effect of nanohydroxy apatite incorporation into the resin infiltrant on its properties. Materials and methods: The total sample size in the three groups was 60 specimens. The specimens were randomly divided in three main groups (ICON, ICON + 5% NHA, ICON + 10% NHA). Water sorption and solubility were evaluated as defined by ISO 4049 specification. The color stability specimens were evaluated with spectrophotometer. Color change was calculated to determine the extent of color stability between the tested groups. Results: a statistically significant difference was observed among the tested groups relating to the water sorption, solubility and the color stability. Conclusion: This study offers a promising route to greatly enhance resin infiltration treatment regarding its durability and color stability.

INTRODUCTION

Dental caries is considered one of the most prevailing diseases affect humans. The avoidance of dental caries and the remineralization of demineralized surface lesions before restorative interference is the goal of modern dentistry.¹

Enamel demineralization is the first sign of dental caries which jeopardizes tooth health and esthetics. Remineralization of these lesions is capable to arrest and reverse the lesion to healthy enamel tissue. The treatment of these lesions is usually performed with fluoride application. Even so, chronic low-level exposure to fluoride can result in some health problems (cancer, birth defects, bone health problems, gastrointestinal tract problems)

additionally to dental fluorosis. For that reason, it is still essential to seek substitute, effective non-fluoride treatment that can afford an inclusive treatment for caries.^{2,3}

Following the up to date idea of minimal invasive dentistry, resin infiltration recently represented an unconventional approach to arrest demineralised lesions. The infiltration technique consists in using hydrophilic and high flowable, light-cured resins that can infiltrate subsurface micro pores, restraining the path of pathogenic bacteria and by-products and avoiding additional lesion development.^{4,5}

Previous studies have revealed that resin infiltration significantly enhances the micro hardness of initial demineralised lesions. Lately,

* Assistant Professor, Department of conservative Dentistry, College of Dentistry, Mansoura University, Mansoura, Egypt.

the advantages of the resin infiltration technique have been recorded: mechanical reinforcement of demineralized enamel, sealing of superficial porous and demineralized areas, and detain of lesion progress by increasing resistance to demineralization, minimized risk of recurrent caries and elevated patient acceptance.⁶⁻⁸

Introduction of nanotechnology to the dentistry has dramatically changed the research areas. The nano-sized particles can be dispersed in higher filler concentration and polymerized into the resin system. Nano-hydroxy apatite (NHA) is considered one of the most biocompatible and bioactive material, and its nano sized particles are similar in morphology, crystal structure and crystalline of tooth enamel. NHA was reported to remineralize artificial caries lesion following its addition to tooth pastes and mouth washes.⁹⁻¹²

Hypothesis:

Incorporation of nanohydroxy apatite with resin infiltrant will have positive impact on its properties.

Objectives:

This study is aimed to assess the influence of nanohydroxy apatite incorporation into the resin infiltrant on its properties.

MATERIALS AND METHODS

Sample size:

The total sample size in the three groups (ICON, ICON + 5% NHA, ICON + 10% NHA) was estimated to be 60 specimens. The specimens were randomly allocated in three test groups.

Specimens' preparation:

Nano hydroxy apatite (NHA, (SIGMA-ALDRICH-USA) resin infiltration were prepared by adding Nano hydroxy apatite powder to the resin infiltration materials (ICON, DMG, Hamburg, Germany) in ratio of 5%, and 10% by weight using

electric digital scale (AG245 Metter, Switzerland). The powder was mixed with resin using electric mixer.

In group I: resins infiltration (RI), without NHA, group II: 5% of NHA resin infiltration (5%NRI) while in group III: 10% of NHA resin infiltration (10%NRI) were employed.

NRI were prepared by adding NHA powder to the resin infiltration materials (Icon) in ratio of 5%, and 10% by weight using electric digital scale. The entire materials were mixed by dual centrifugal laboratory vacuum mixer system (SpeedMixer.co.uk) for one min at speed 1300 rpm. Photo activation process for the resin were done by a light emitting diode (LED) light curing unit (LEDition, ivoclar vivadent, Austria). The curing was applied for 20 sec on each side, with the tip away of one mm.

Water sorption (Wsp) and solubility (Wsl):

For specimens preparation the resin was applied in a teflon mold with 12 mm diameter and 1mm thick. The mold was positioned between clear strips and glass slides under pressure, any excess material was removed. The cured specimens were stored in dark and dry container for 24 h, and afterward relocated to desiccators at $37 \pm 1^\circ\text{C}$. After 22 h in the first desiccators, the specimens were transferred to second desiccators for 2 h at $25 \pm 1^\circ\text{C}$, and then the weight of each specimen was recorded using an electric digital scale. In anticipation of a constant mass (m1) was gained (the variation was less than a ± 0.0001 g) the cycle was repeated. Then the specimens were immediately immersed in deionized water at $37 \pm 1^\circ\text{C}$, and measurements were obtained again after 60 days (m2). Following this step, the specimens were subjected to the previously mentioned process to gain a constant dry mass (m3), as the cycle described for m1. The values of (Wsp) and (Wsl) were calculated by the following equations as mentioned by ISO 4049 specification¹³:

$$W_{sp} = 100 \times ((m_2 - m_1)/m_1)$$

$$W_{sl} = 100 \times ((m_1 - m_3)/m_1)$$

Color stability:

The oval disc shaped specimens were fabricated in teflon mold 12 X10 mm in diameter and 2 mm in thickness as required by ISO International Standard #7491:2000.¹⁴ After curing, specimens were stored in dry and dark container at 37°C for 24 h. Color readings were recorded 24 h after polymerization (baseline) and second reading after 60 days of immersion in distilled water at 37°C in dark container. Water excess was removed from the specimens before readings by blotting papers. Water medium were changed weekly. Spectrophotometry (Color-Eye 7000A spectrophotometer, X-rite, Grand Rapids, Michigan, USA) was used to determine the color values consistent with The CIELab system (Commission International de l’Eclairage L*a*b*). The original color measurement was recorded after 24 hours immersion in distilled water for each specimen as base line measurements. CIE-Lab is conveyed by the L* coordinate, stand for color luminosity, varying from white to black; and the a* and b* coordinates, stand for the chromaticity of the color, with axes varying from green to red and blue to yellow, respectively. This color space is illustrated by a sphere, where the Y axis stands for the L* parameter (lightness, from 0 = black, up to 100 = white), the X axis is the b* parameter (from -b = blue, up to +b = yellow) and the Z axis represents the a* parameter (from -a = green, up to +a = red), The match of these coordinate outcomes a spatial position that mathematically represents the color. All documented values were based on D65 illuminant and 10° observer geometry. For calibration, the spectrophotometer was adjusted over white and black backgrounds. Three measurements were done in the top surface of each specimen. The color changes (ΔE) were mathematically calculated by using the following formula.¹⁵

$$\Delta E = [(\Delta L^*)^2 + (\Delta a^*)^2 + (\Delta b^*)^2]^{1/2};$$

Where $\Delta L = L$ (60 days) – L (baseline),

$\Delta a = a$ (60 days) – a (baseline),

And $\Delta b = b$ (60 days) – b (baseline); where “baseline” values were obtained 24 h after the photo activation process.

Statistical analysis:

Numerical data were checked for normality by evaluating the distribution of data and using tests of normality (Kolmogorov-Smirnov and Shapiro-Wilk tests). Water solubility and sorption data showed normal (parametric) distribution on the other hand color parameters data showed non-parametric distribution. Parametric data were presented as mean, standard deviation (SD), 95% Confidence Interval values while non-parametric data were presented as median and range values. For parametric data, one-way Analysis of Variance (ANOVA) was used to compare between the groups. Bonferroni’s post-hoc test was used for pair-wise comparisons. For non-parametric data; Kruskal-Wallis test was used to compare between the three groups. Dunn’s test was used for pair-wise comparisons.

The significance level was considered at $P \leq 0.05$. Statistical analysis was performed with IBM (IBM Corporation, NY, USA), SPSS (SPSS, Inc., an IBM Company) Statistics Version 20 for Windows.

RESULTS

Water solubility

There was a statistically significant difference between the groups (P-value <0.001, Effect size = 0.943). Pair-wise comparisons between the groups showed that RI group statistically scored the highest mean solubility. 5% NRI group showed lower mean value. While 10% NRI group showed statistically the lowest mean water solubility.

TABLE (1) Descriptive statistics and results of one-way ANOVA test for comparison between water solubility (%) of the three groups

	RI	5% NRI	10% NRI	P-value	Effect size (Eta Squared)
Mean (SD)	6.74 (0.61) ^A	4.92 (0.93) ^B	0.81 (0.08) ^C	<0.001*	0.943
95% CI	6.3 – 7.17	4.26 – 5.59	0.75 – 0.87		

*: Significant at $P \leq 0.05$, Different superscripts are statistically significantly different

TABLE (2) Descriptive statistics and results of one-way ANOVA test for comparison between water sorption (%) of the three groups

	RI	5% NRI	10% NRI	P-value	Effect size (Eta Squared)
Mean (SD)	31.17 (1.51) ^A	15.3 (0.86) ^B	10.81 (0.48) ^C	<0.001*	0.987
95% CI	30.09 – 32.24	14.68 – 15.91	10.47 – 11.15		

*: Significant at $P \leq 0.05$, Different superscripts are statistically significantly different

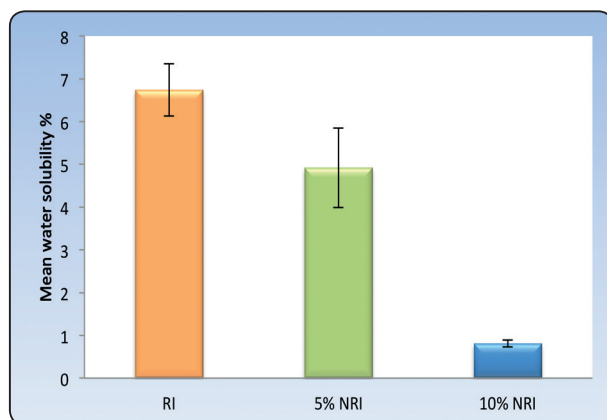


Fig. (1) Bar chart representing mean and standard deviation values for water solubility %

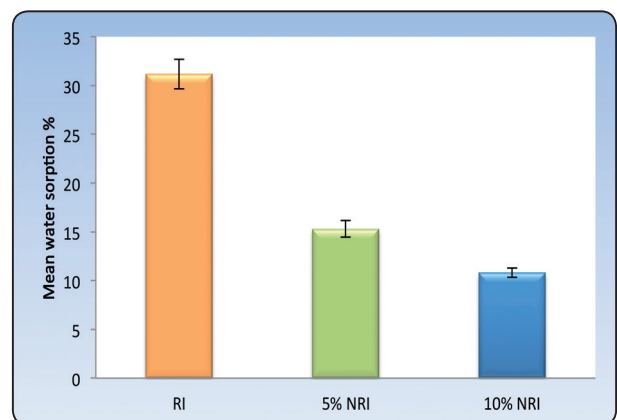


Fig. (2) Bar chart representing mean and standard deviation values for water sorption %

Water sorption

There was a statistically significant difference between the tested groups (P -value <0.001, Effect size = 0.987). Pair-wise comparisons between the groups revealed that RI group showed statistically the highest mean sorption. 5% NRI group showed lower mean value. 10% NRI group showed the lowest mean water sorption.

Color parameters

As regards ΔL ; there was a statistically significant difference between the tested groups (P -value = 0.013, Effect size = 0.247). Pair-wise comparisons between the groups showed that RI group statistically recorded the highest median ΔL . 10% NRI group scored lower median value. 5% NRI group was graded the statistically significantly lowest median ΔL .

As regards Δa ; there was a statistically significant difference between the tested groups (P -value <0.001 , Effect size = 0.492). Pair-wise comparisons between the groups showed that RI group has the highest median ΔL . 5% NRI group showed lower median value. 10% NRI group was the statistically significantly lowest median Δa .

While for Δb ; no statistically significant difference between the groups was observed (P -value = 0.188, Effect size = 0.050).

As regards ΔE ; there was a statistically significant difference between the tested groups (P -value <0.001 , Effect size = 0.616). Pair-wise comparisons between the groups showed that RI

group has the highest median ΔE . 5% NRI group showed lower median value. 10% NRI group has the statistically significantly lowest median ΔE .

DISCUSSION

The most significant properties determining the durability and longevity of dental restorations in the oral cavity is dimensional stability against dissolution and disintegration. The most common laboratory test of solubility is the ADA specification No. 8 (American Dental Association) which was followed in this study. Resin monomers are the principal chemical components of composite restorative materials. Both acrylates and methacrylates monomers are susceptible to water degradation (hydrolysis) of

TABLE (3) Median, range values and results of Kruskal-Wallis test for comparison between color parameters of the three groups

	RI	5% NRI	10% NRI	P -value	Effect size (Eta Squared)
ΔL	2.18 (-1.35 – 3.56) ^A	-0.65 (-2.99 – 2.24) ^C	0.67 (0.32 – 0.92) ^B	0.013*	0.247
Δa	-0.97 (-1.79 - -0.19) ^A	-0.41 (-0.98 – 0.37) ^B	-0.12 (-0.21 - -0.03) ^C	<0.001 *	0.492
Δb	-5.67 (-10.03 – 3.81)	-0.82 (-5.93 – 3.81)	-0.28 (-0.89 - -0.08)	0.188	0.050
ΔE	6.28 (2.15 – 10.41) ^A	3.29 (0.61 – 6.32) ^B	0.79 (0.39 – 1.15) ^C	<0.001 *	0.616

*: Significant at $P \leq 0.05$, Different superscripts in the same row are statistically significantly different

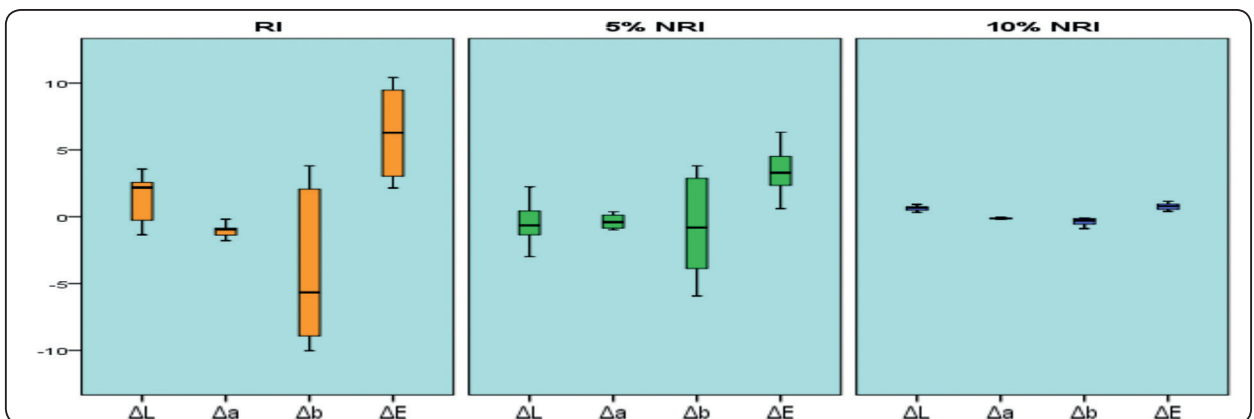


Fig. (3) Box plot representing median and range values for color parameters in the three groups

their ester group. Due to its hydrophilicity it may lead to water uptake, which primes to higher hydrolysis susceptibility of the monomers along with discoloration of the cured resin.¹⁶

Although TEGDMA revealed the best ability to infiltrate deep into the demineralized caries lesion.⁶ It has been reported that, TEGDMA has the most water sorption affinity, followed by BisGMA and by UDMA. Thus, in this study TEGDMA resin monomer is the main compositions of the resin infiltration. This may explain the tendency of the icon to water sorption and solubility. Additionally, the resin infiltration Icon does not include any filler leads to its higher susceptibility to water sorption and solubility than the groups with NHA fillers.¹⁷

Maintaining color stability in the oral cavity is a fundamental property for tooth colored restorative materials. Even though improvements have been accomplished recently, discoloration is still a problem.¹⁸

Many researches approved the effectiveness of the infiltration treatment technique with Icon of non-cavitated caries lesions.^{4,5} Though, maintaining color stability of the resin over time is mandatory.¹⁹

The method in the present study was in accord with several researches that used spectrophotometry and the CIE L*a*b* coordinate system, which is a widely used tool for dental purposes. Many studies recorded the advantages of the CIE L*a*b* coordinate system, for instance its repeatability, sensitivity, and objectivity.¹⁹ This technique was preferred in evaluation the color change (ΔE) because its ability for the detection of small color variations.²⁰ ΔE values between 1 and 3 are perceptible to the naked eye and ΔE values greater than 3.3 are considered clinically unacceptable.²¹⁻²³

In this study, although all the materials tested have demonstrated color changes after the immersion time; some variances have revealed between the tested materials. Icon recorded significantly higher variation in ΔL (lightness) and Δa (green-red component) values. Regarding

the total color changes (ΔE), Icon also scored the highest values (ΔE 6.28) which can be considered clinical unacceptable. This may be explained by a breakdown of the matrix components overtime degradation of the resin coupled with water sorption of TEGDMA, which leads to resin discoloration.²⁴

Hence, in this study Icon (composed mainly of TEGDMA and not include any filler) became more discolored as compared with other groups.

Our results are in accordance with recent studies, which observed that Icon presents significant alteration of color after staining procedures.^{25, 26} On the other hand clinical studies, concluded the acceptable color stability of resin infiltration in the oral environment, These Authors revealed that the color stability can be achieved by polishing to remove any stain.^{27,28}

In the present study, a long-term exposure with specimens stored for 60 days in distilled water was performed, which is considered sufficient for long-term staining ability evaluation.²⁹

CONCLUSION

Results concluded from the present study could be of clinical relevance. It is contemplated that while Icon can enhance the esthetic problem associated with demineralization, the resin may discolored over time, nevertheless, this has been investigated on pure Icon discs without the underlying tooth structures.

Incorporation of NHA with Icon will enhance its color stability and decrease its water sorption and solubility.

REFERENCES

1. Gorelick I, Geiger AM, Gwinnet AJ. Incidence of white spot formation after bonding and banding. *Am J Orthod* 1982; 81:93-8.
2. Artun J, Brobakken B. Prevalence of caries and white spots after orthodontic treatment with multibonded appliances. *Eur J Orthod* 1986; 8:229-34.

3. Artun J, Thylstrup A. A 3-year clinical and SEM study of surface changes of carious enamel lesions after inactivation. *Am J OrthodDentofacial Ortho* 1989; 95:327-333.
4. Paris S, Meyer-Lueckel H. Masking of labial enamel white spot lesions by resin infiltration: a clinical report. *Quintessence Int.* 2009; 40:713-8.
5. Paris S, Meyer-Lueckel H. Inhibition of caries progression by resin infiltration in situ. *Caries Res.* 2010; 44:47-54.
6. Paris S, Schwendicke F, Seddig S, Müller WD, Dörfer C, Meyer-Lueckel H. Micro-hardness and mineral loss of enamel lesions after infiltration with various resins: Influence of infiltrant composition and application frequency in vitro. *J Dent.* 2013; 41:543-48.
7. Taher NM, Alkhamis HA, Dowaidi SM. The influence of resin infiltration system on enamel microhardness and surface roughness: An in vitro study. *Saudi Dent J.* 2012; 24:79-84.
8. Paris S, Lausch J, Selje T, Dörfer CE, Meyer-Lueckel H. Comparison of sealant and infiltrant penetration into pit and fissure caries lesions in vitro. *J Dent.* 2014; 42:432-8.
9. Pendrys DG. Dental fluorosis in perspective. *J Am DentAssoc.* 1991; 122:63-66.
10. Lu KL, Zhang JX, MengXc, Li XY. Remineralization effect of the nano-HA tooth paste on artificial caries. *KeyEng Mater.* 2007; 330-332:267-270.
11. Kim MY, Kwon HK, Choi CH, Kim BL. Combined effect of nano-HA and NaF on remineralization of early caries lesion. *Key Eng Mater.* 2007; 330-332:1347-1350.
12. Huang SB, Gao SS, Yu HY. Effect of nano-HA concentration on remineralization of initial enamel lesion in vitro. *Biomed Mater* 2009; 4(3):034104.
13. International Organization for Standardization. ISO4049:2000 - Polymer-based filling, restorative and luting materials. Geneva: ISO; 2000, 28 p.
14. Gürdal, P., B. Güniz, Akdeniz and S.E.N. Hakan, The effects of mouthrinses on microhardness and color. *Journal of Oral Rehabilitation*, 2002; 29: 895-901.
15. Vichi A, Ferrari M, Davidson CL. Color and opacity variations in three different resin-based composite products after water aging. *Dent Mater* 2004; 20:530-4.
16. Van Landuyt KL, Snauwaert J, De Munck J, Peumans M, Yoshida Y, Poitevin A. Systematic review of the chemical composition of contemporary dental adhesives. *Biomater.* 2007; 28: 3757-85.
17. Sideridou I, Tserki V, Papanastasiou G. Study of water sorption, solubility and modulus of elasticity of light-cured dimethacrylate-based dental resins. *Biomater.* 2003; 24: 655-65.
18. Villalta P, Lu H, Okte Z, Garcia-Godoy F, Powers J. Effects of staining and bleaching on color change of dental composite resins. *J Prosth Dent.* 2006;95:137-42
19. Hammad SM, El Banna M, El Zayat I, Mohsen MA. Effect of resin infiltration on white spot lesions after debonding orthodontic brackets. *Am J Dent.* 2012; 25:3-8
20. ElEmbaby A el-S. The effects of mouth rinses on the color stability of resin-based restorative materials. *J Esthet Restor Dent* 2014 Jul-Aug;26(4):264-71.
21. Brook AH, Smith RN, Lath DJ. The clinical measurement of tooth color and stain. *Int Dent J.* 2007; 57:324-30.
22. AlSheikh R, El-Embaby AE. Spectrophotometric Comparison of Effectiveness of Two In-office Bleaching Agents with/without Light Activation: A Clinical Study. *J Contemp Dent Pract.* 2018; 1; 19(6):637- 41.
23. Bagheri R, Burrow MF, Tyas M. Influence of food-simulating solutions and surface finish on susceptibility to staining of aesthetic restorative materials. *J Dent* 2005; 33: 389-398.
24. Sabatini C, Campillo M, Aref J. Color stability of ten resin-based restorative materials. *J EsthetRestor Dent* 2012; 24:185-199.
25. Borges A, Caneppele T, Luz M, Pucci C, Torres C. Color stability of resin used for caries infiltration after exposure to different staining solutions. *Oper Dent.* 2014; 39:433-40
26. Rey N, Benbachir N, Bortolotto T, Krejci I. Evaluation of the staining potential of a caries infiltrant in comparison to other products. *Dent Mater J.* 2014; 33:86-91.
27. Knosel M, Eckstein A, Helms HJ. Durability of esthetic improvement following Icon resin infiltration of multibracket-induced white spot lesions compared with no therapy over 6 months: a single-center, split-mouth, randomized clinical trial. *Am J Orthod Dentofacial Orthop.* 2013; 144:86-96.
28. Eckstein A, Helms HJ, Knosel M. Camouflage effects following resin infiltration of postorthodontic white-spot lesions in vivo: One-year follow-up. *Angle Orthod.* 2015; 85:374
29. Ertas E, Guler AU, Yucel AC, Koprulu H, Guler E. Color stability of resin composites after immersion in different drinks. *Dent Mater J.* 2006; 25:371-76.