

FRICITION AND VIBRATION ANALYSIS OF SLIDING SURFACES LUBRICATED BY ENGINE OILS DISPERSED BY ALUMINUM OXIDE NANOPARTICLES

Rashed A. and Nabhan A.

**Department of Production Engineering and mechanical Design, Faculty of Engineering, Minia University,
El-Minia 61111, Egypt.**

ABSTRACT

The present investigation is focusing on the enhancement of tribological properties of 20W-50 engine oil by the addition of Al₂O₃ nanoparticles. The frictional property of engine oil was investigated by tribometer using stainless steel disc and plate. It was found that Al₂O₃ added to engine oil enhanced coefficient of friction significantly and reduced vibrations. The study concluded that the lowest coefficient of friction was obtained at 0.4 wt. % concentration of Al₂O₃ nanoparticles and working temperature of 50 °C. The lowest and highest acceleration values were detected for oil at 50 and 100 °C operating temperatures respectively.

KEYWORDS

Friction, vibration analysis, Al₂O₃ nanoparticles, lubricant additives, engine oils.

INTRODUCTION

The tribological characteristics of the 5W-30 engine oil by adding CranAlc MAX Nano lamella was studied, [1]. The anti-wear resistance of engine oil were examined by four-ball test device using stainless steel balls. The results obtained were compared with h-BN and MoS₂ nanoparticles that included 5W-30 engine oils. The added Cr₂AlC fluid (modified lubricant) significantly enhances anti-wear properties and increases the strength of the oil film (OFS) from the base oil to approximately three times. The performance of Nano-lanthanum hydroxide/reduced graphene oxide compounds (Nano-la (OH)₃/RGO) has been successfully studied as anti-wear additives for diesel engine oil, and the results indicate that Nano-la (OH)₃/RGO compounds can significantly improve performance diesel engine oils under boundary lubrication conditions, [2]. In particular, the wear resistance performance of diesel engine oil increased by 44 % after the addition of a compound by 0.1% by weight at 80 ° C and contact pressure of 1.62 GPa. Huawei Wu et al.

A study aimed to evaluate the thermal experiment for the thermal conductivity of mixed nanofluoride from zinc oxide (ZnO) and multi-wall CNT (MWCNT) in engine oil (SAE

10W40), [3]. The effects of the concentration of nanoparticles as well as the temperature of the liquid are evaluated. Experiments were conducted at a temperature between 25 and 50 °C and the nanoparticle fraction size from 0.05 to 0.8%. Experimental results showed that a higher percentage of thermal conductivity of lubricating nanoparticles is achieved to obtain a higher portion size and temperature of nanoparticles. The mechanics behind high friction using an integrated methodology, based on atomic force microscopy (AFM) and optical X-ray spectroscopy (XPS) were examined, [4, 5]. The use of the analytical contact mechanics model shows that the compression coefficient of the border shear force, measured using a lateral force microscope, provides an explanation for the observed increase in friction measured on a micro-scale.

Presentation of a feasibility study for the use of a new nanoparticle oil containing a mixture of MWCNT - nanoparticles arranged by 30 - 70% was introduced, [6]. The results of the experimental study showed a significant reduction in the viscosity of motor oil nanoparticles (as compared to the viscosity of pure 5W50 oil) after the addition of 0.05% and 0.1% of nanoparticles to 5W50. Reducing the viscosity reduces the damage caused by starting the engine in case of cold start. The results of test activities performed on a fully formulated motor oil incorporating MoS₂ nanoparticles were described, [7]. Nanoparticles were allowed to appear in the new European driving cycle (NEDC) to reduce fuel consumption by 0.9 % for reference lubricants without the presence of nanoparticles. It was observed that both the wear resistance and high-pressure properties of castor oil specimens were enhanced with the addition of ZnO nanocomposition rates to a certain concentration of zinc oxide nanoparticle friction rates (0.1 %), which were then not significantly improved in coefficient of friction observed but increased wear rate, [8]. The formation of a triple-core film due to adsorption and adherence to nano-friction rates on surfaces was responsible for reducing corrosion properties.

The dispersal of MWCNTs nanoparticles and zinc oxide nanoparticles containing a fraction of 0.005% and 0.02%, respectively, were studied together with surface gum Arabic in SAE 20W40 engine oil, [9]. Tribological properties such as wear resistance, friction coefficient and thermal-physical properties such as thermal conductivity, viscosity, and flash point for nano-lubricating oils were evaluated and compared with normal engine oil properties. Thus, the results show that the marked improvement in the operational properties of engine oil is due to the dispersion of nanoparticles in it. It was observed that the viscosity of nanofluid increases with the reduction of solid volume fraction, [10]. Moreover, it was found that as the temperature rises, the viscosity of the nanofluids decreases, and they are more noticeable at lower temperatures. Comparison of experimental results with theoretical models showed that these models failed to predict the correct viscosity values of nanofluids in all solid volume fractions. Experimental data also indicated that the maximum viscosity of nanofluid was 132% compared to the base fluid. The mixing of TiO₂ nanoparticles in engine oil significantly reduces the rate of friction and corrosion and thus improves the lubricating properties of engine oil, [11, 12]. The analysis of TiO₂ nanoparticle dispersion in lubricating oil using a UV spectrometer shows that TiO₂ nanoparticles have good stability and solubility in lubricant and improve lubricating properties of engine oil.

The effect of adding SiO₂ and TiO₂ nanoparticles to mineral oils (20W-50) and (15W-50) on the tribological behavior was carried out using tribometer setup under different working temperatures, 40, 80 and 100 °C, [13]. The friction coefficient and wear rate reduce with lubricant oils of 1.0% wt. of TiO₂ content. While, oil samples contain of SiO₂ nanoparticles have not a great role in improving of the tribological behavior, [14]. The variation of the concentration of Al₂O₃ nanoparticles with jojoba oil was assessed for tribological properties. It was observed that the minimum coefficient of friction and corrosion at a concentration of 0.1% is increasing at a concentration of 0.15 % and the maximum corrosion was obtained at a concentration of 0.2%.

It was aimed to study the effect of the addition of Al₂O₃-Fe₂O₃ hybrid Nano powder on the thermal properties of 10w40 engine oil, [15]. The results indicated that even the smallest concentration of the mass improves the thermal properties of lubricating nanoparticles. A study to assess the tribological properties of ZODDP as a diacosyl sephakate additive (DIOS) in steel and aluminum contacts on the ball scale on the disc was carried out, [16]. Compared with ZDDP, the friction coefficient and corrosion rate of ZODDP decreased by 10.37 % and 71.74 % respectively, [17]. Al-SiC-nAl₂O₃-WS₂ was prepared by powder metallurgy method and nano-alumina by combustion process solution.

The present work aims to enhance the tribological properties of 20W-50 engine oil by addition of Al₂O₃ nanoparticles. The frictional property of engine oil was investigated by tribometer using stainless steel disc and plate.

EXPERIMENTAL

The Tribometer Test-Rig

Friction tests were performed experimentally using a tribometer. It is designed to simulate, evaluate and test almost all types of oil, as shown in Fig. 1. The testing machine contains aluminum friction plates used to measure friction force. Engine oil was used without additive as reference lubricant. Tests were performed using flat-panel pin specimens in the contact area, where the applicable rotational speed was from 1,000 to 3,000 rpm. Experiments were conducted using the tested oil heated to 50, 75 and 100 °C temperatures. Before each test, the disc holder and the lifting stand were cleaned to get rid of unwanted materials such as foil or lubricants stuck to the contact surfaces. The test was generally used as a comparative test in which the coefficient of friction is measured over the specimens to be studied. The vibration setting is used in this work to record velocity and acceleration signals to study the acceleration generated by a different mechanism with a five-band vector. Optical coding is used to measure shaft speed. Thus, the rotational speed of the shaft is known directly from this console reading. Flexible clutch coupling is used to remove the high-frequency vibration caused by the motor. Two balls are installed in solid housings. Accelerometers (IMI Sensors- 603C01) are installed on a tested bearing housing to measure acceleration signals in two directions. A data acquisition card (BMC USB-AD16F) is used to collect signals.

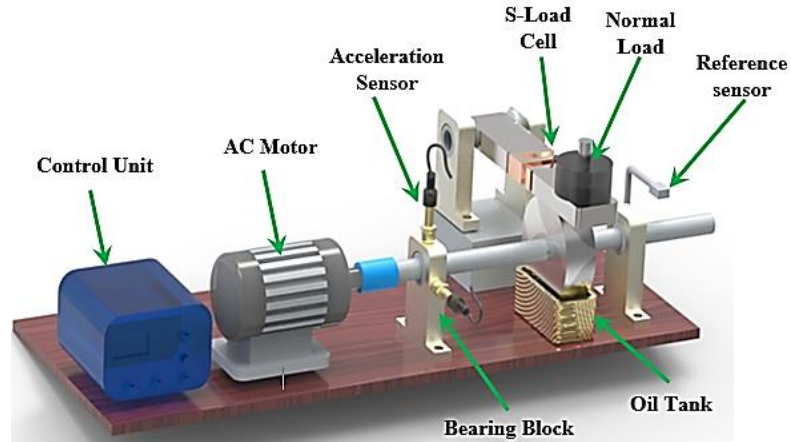


Fig. 1 Representation of the tribometer and vibration test rig.

Preparation and Fabrication of Specimens

Engine oil (20W-50) is used. Then, concentrations of Al_2O_3 nanoparticles of 0.1, 0.2, 0.3 and 0.4 wt. % were used. Good stirring was taken into consideration to ensure uniform distribution of the nanoparticles in the tested oil. Figure 2 shows test specimens of lubricating oils mixed in different temperatures, where the temperatures of the mixing process was 50, 100 and 150 °C in order to study the effect of the mixing temperature on the friction coefficient and the damping ratio in the resulting vibrations.



Fig. 2 Oil samples mixed with Al_2O_3 nanoparticles at temperature (a) 50°C, (b) 100°C and (c) 150°C.

RESULTS AND DISCUSSION

Engine oil acts as a lubricant by reducing the friction coefficient between the sliding parts of the engine and thereby reducing fuel consumption. It also acts as a coolant by carrying excess heat away from the moving parts of the engine, Fig. 3. The heat stored in large quantities of engine oil is usually higher than the thermal conductivity that leads to the

formation of oil sludge inside the engine in extreme conditions and increases the chances of burning engine oil and thus producing a large amount of smoke.

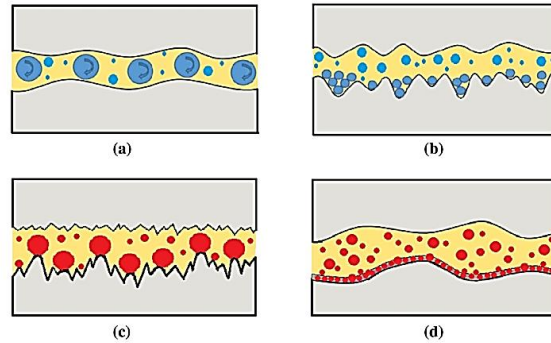


Fig. 3 Different mechanisms for the tribological performance using nanoparticles (a) rolling mechanism; (b) mending mechanism; (c) polishing mechanism; (d) protective film, [18, 19].

Analysis of Friction Coefficient

The effect of friction coefficient was studied with different speeds for a set of test specimens of engine oils to which a percentage of Al_2O_3 nanoparticles were added. Figure 4 shows the effect of the friction coefficient at different velocities of the tested specimens at 50°C . The specimens were mixed at 50°C . It was observed that the friction coefficient significantly decreased with an increase in the content of Al_2O_3 nanoparticles. The Al_2O_3 contents 0.1 and 0.2 wt. % are closely related. There has been a clear reduction of the friction coefficient for 0.4 wt. % content at relatively high speeds under all operating temperatures and this may be due to rolling effect of nanoparticles generated at the rubbing surfaces. The Al_2O_3 nanoparticles may be able to form a thin-layer between asperity contacts helps to reduce of the shear stress and friction coefficient to prevent the metal-metal contact. Generally, with the increase in operating temperatures, an increase in the friction coefficient is observed, while the decrease in the coefficient of friction with the increase in the ratio of the Al_2O_3 nanoparticles was dominating, Fig. 5. This may be due to lower viscosity of the engine oil when operating temperature increased.

Figures 6 and 7 show a lower value of coefficient of friction for all contents of Al_2O_3 than that observed for tested oil free of nanoparticles. The lowest coefficient of friction for all concentrations values were observed at 100°C mixing temperature at 0.3 wt. % Al_2O_3 nanoparticles. It was observed that the lowest friction coefficient was reached at 50°C working temperature. It can be concluded that, at different temperatures and rotational speeds, Al_2O_3 nanoparticle additives with concentration of 0.3 wt. % at 100°C mixing temperature can efficiently improve the lubricating properties of the engine oil.

At 150°C mixing temperature, Figs. 8 and 9, friction coefficient of the highest Al_2O_3 content was close to the friction coefficient of pure oil, while the lowest friction coefficient was at 0.2 wt. % Al_2O_3 nanoparticles.

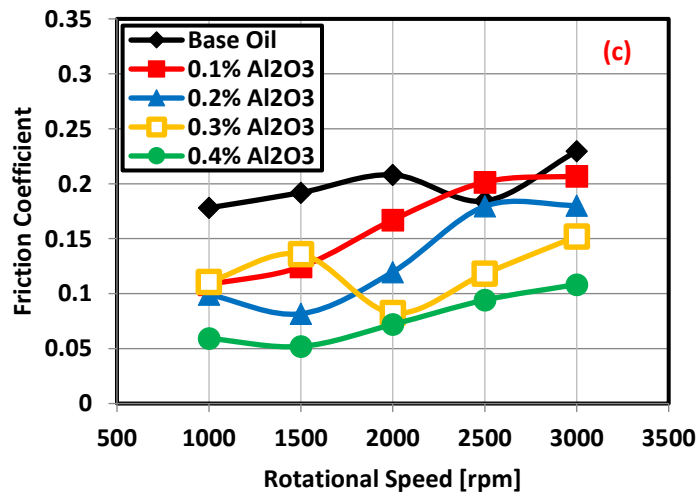
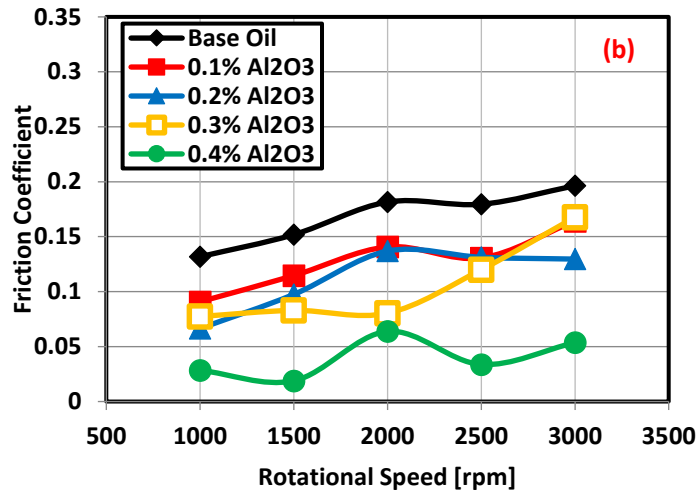
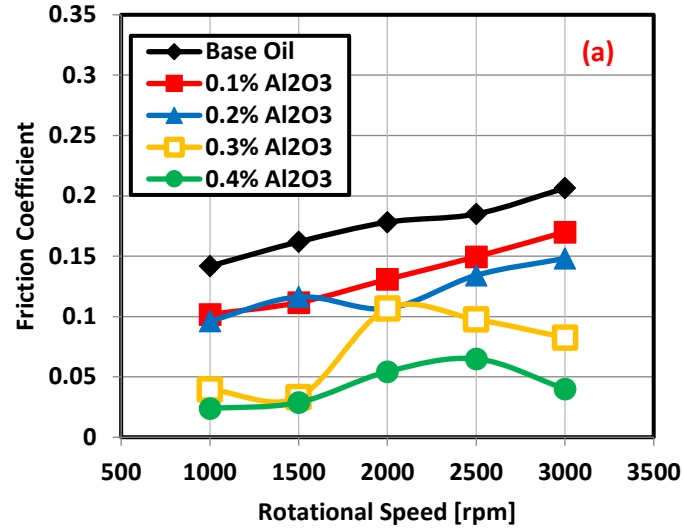


Fig. 4 Friction coefficient with different rotational speed for Al₂O₃ mixed at temperature 50°C and operating at temperatures (a) 50°C, (b) 75°C and (c) 100°C.

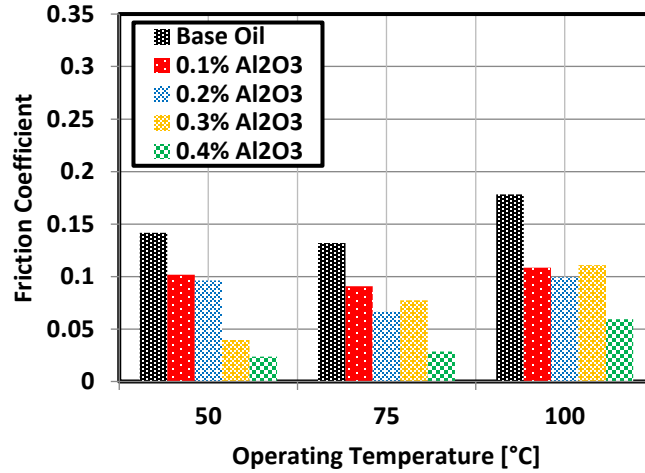


Fig. 5 Friction coefficient observed at different operating temperatures at 50°C mixed temperature.

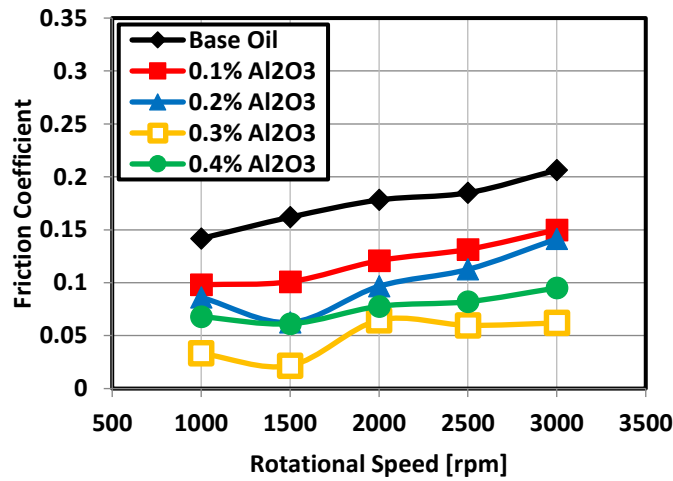


Fig. 6 Friction coefficient Friction coefficient with different Rotational Speed for Al₂O₃ mixed at 100°C temperature and operating at 50°C temperature.

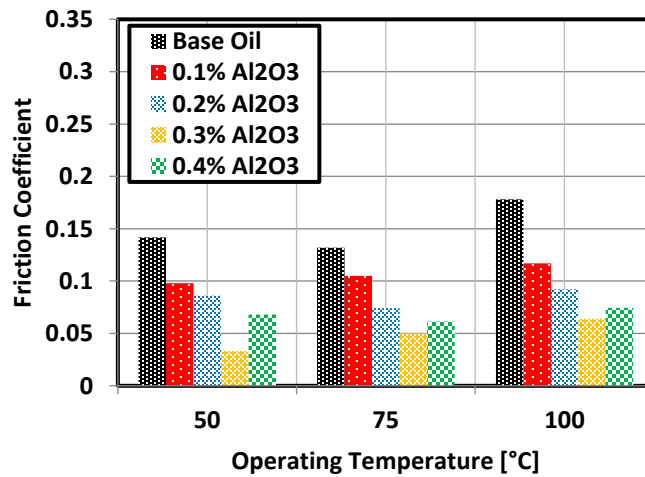


Fig. 7 Friction coefficient observed at different operating temperatures at 100°C mixed temperature.

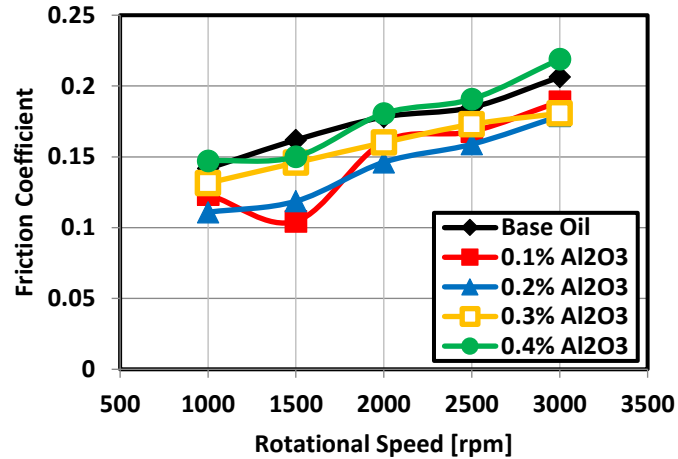


Fig. 8 Friction coefficient with different rotational speed for Al₂O₃ mixed at 150°C temperature and operating at 50°C temperature.

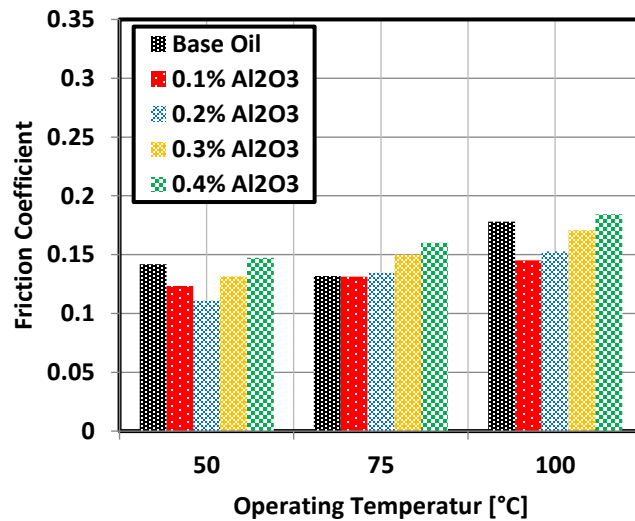


Fig. 9 Friction coefficient observed at different operating temperatures at 150°C mixed temperature.

To find out the effect of the mixing temperature of nanoparticles on the friction coefficient, a comparison was made. The various samples content of Al₂O₃ nanoparticles, is carried out under operating conditions of a speed of 1000 rev/min and operating temperature of 75°C, as illustrated in Fig. 10. It can be observed that the increasing of mixing temperature leads to increase of the friction coefficient with all content adding. It may be due to the increase in temperature, which reduces the oil viscosity, which impedes the dispersion and the suspending of nanoparticles through the oil. Therefore, it is possible to notice the presence of the particles deposits in the bottom of the container. The particles agglomerating will lead to rise oil thickening, which causes an increase in the friction coefficient of the bearing surfaces. Therefore, it can be concluded that 50°C is the best mixing temperature.

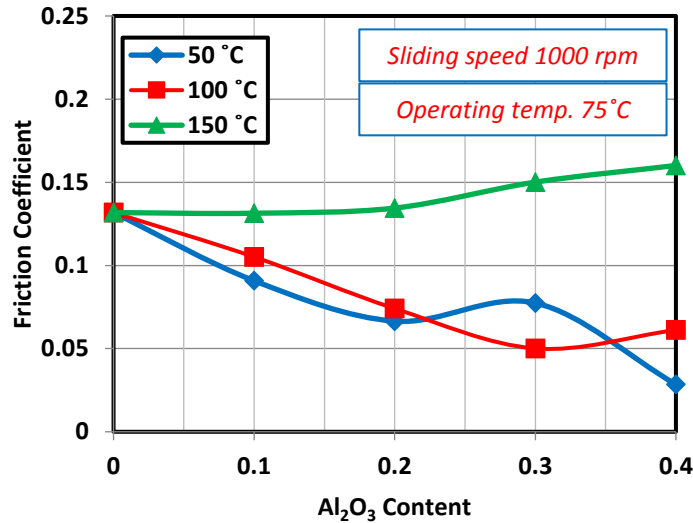


Fig. 10 Comparison of the effect of mixing temperature on the friction coefficient at different Al₂O₃ content

Analysis of Vibration

The value of the acceleration with the different rotational speed of the oil mixed with the nanoparticles at 50 °C temperature is shown in Figs. 11 and 12. It was observed that the lowest value of the acceleration was recorded at 0.4 wt. % Al₂O₃ content at 50 °C working temperature due to the high viscosity of the oil maintaining at the lower temperature. The highest value of vibrations was recorded for oil free of nanoparticles, where the increase in the content of nanoparticles was followed by an increase in the value of damping. The lowest value of acceleration amplitude (RMS) was obtained at 0.4 wt. % Al₂O₃ content and at 50 °C working temperature, while the highest vibrations reached at clean oil at 100 °C working temperature due to the low viscosity.

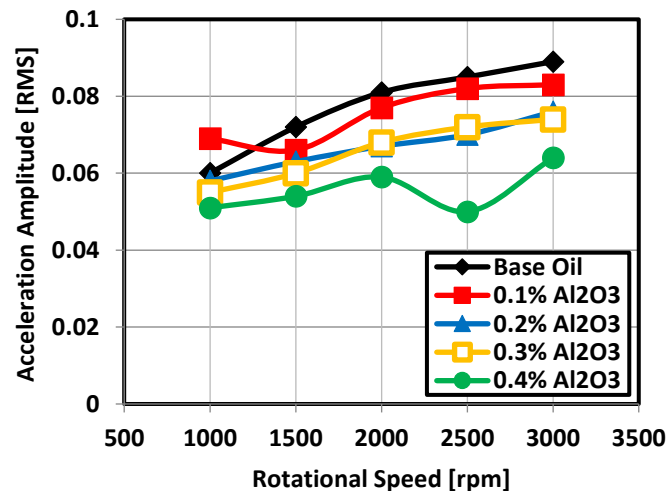


Fig. 11 Acceleration Amplitude [RMS] with different rotational speed for Al₂O₃ mixed at 50°C temperature and operating at 50°C temperature.

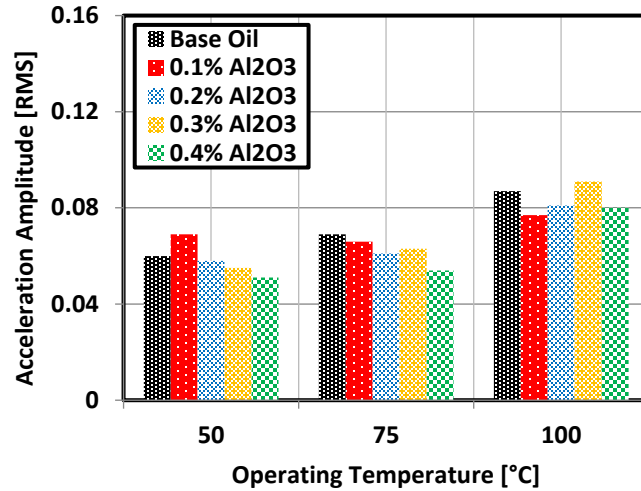


Fig. 12 Comparison between different operating temperatures for oil at 50°C mixed temperature.

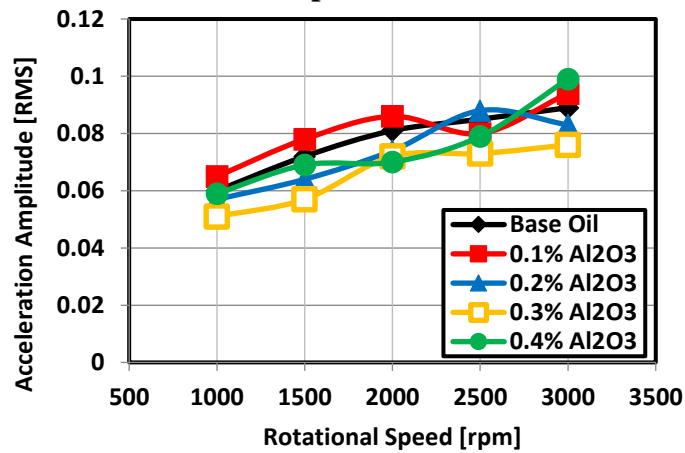


Fig. 13 Acceleration amplitude [RMS] with different rotational speed for Al₂O₃ mixed at 100°C temperature and operating at 50°C temperature.

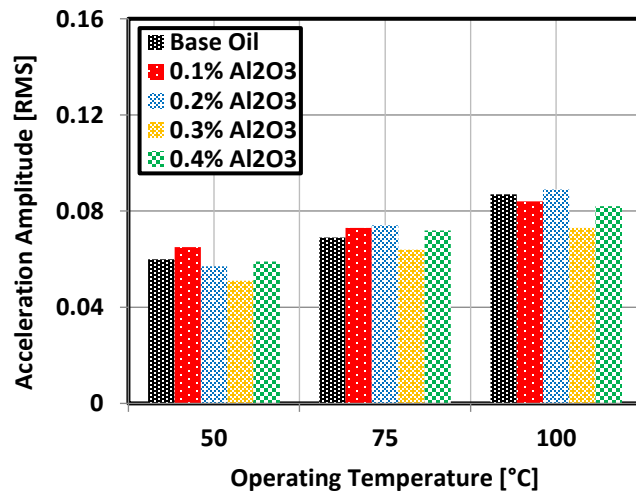


Fig. 14 Comparison between different operating temperatures for oil at mixed 100°C temperature.

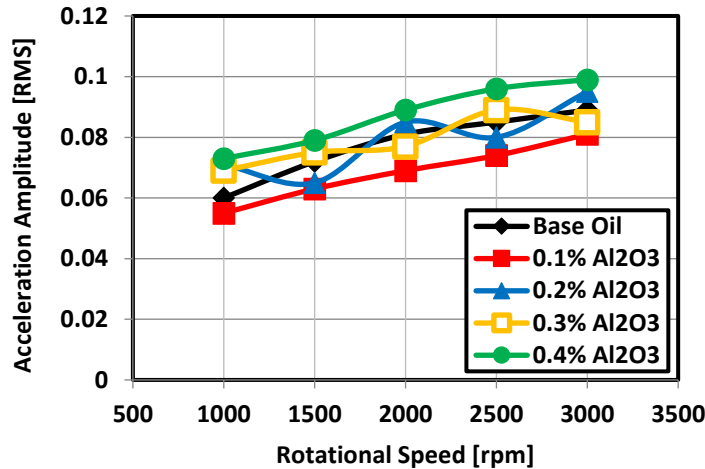


Fig. 15 Acceleration amplitude [RMS] with different rotational speed for Al₂O₃ mixed at 150°C temperature and operated at 50°C temperature.

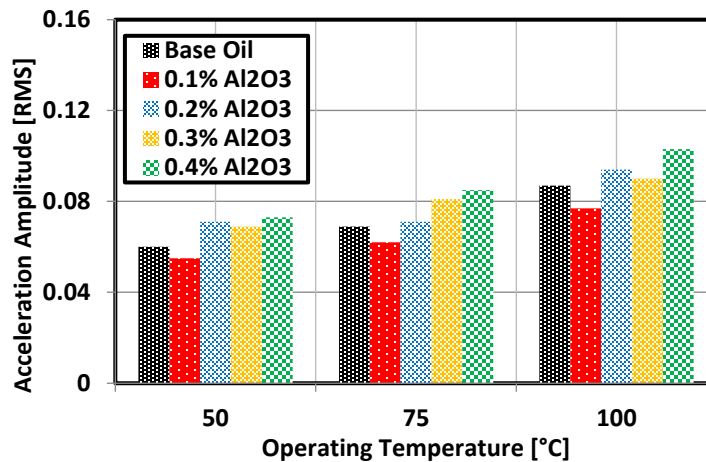


Fig. 16 Comparison between different operating temperatures for oil at 150°C mixed temperature.

The variations of acceleration amplitude [RMS] with different rotational speed for Al₂O₃ mixed at temperature 100 and 150°C are shown in Figs. 13 – 16. At mixing temperature of 100°C, it can be observed that the oil of 0.3 wt. % Al₂O₃ content has lowest RMS values. While it is illustrated, for samples mixed at temperature 150°C, that the acceleration amplitude (RMS) was measured at 0.4 wt. % Al₂O₃ content higher than the base oil and the lowest vibrations occurred at 0.1 wt. % Al₂O₃ content.

CONCLUSIONS

The tribological behavior and vibration (RMS) of engine oil at different operating temperatures and different Al₂O₃ nanoparticles content was studied. It was found that addition of nanoparticles were found to advance the tribological properties of the existing commercial engine oils (20W - 50). The prepared lubricating oils were found to be stable in the entire analysis period. In addition, the study concluded that the lowest coefficient of friction was reached when mixing under a temperature of 50 ° C and at 0.4 wt. % Al₂O₃

content at a working temperature of 50 °C. In contrast, the highest friction coefficient was reached when mixing under a temperature of 150 °C and 0.4 wt. % Al₂O₃ content at working temperature of 100 °C. The lowest acceleration amplitude (RMS) at mixing was 50 °C, 0.4 wt. % Al₂O₃ content at 50 °C operating temperature. The highest acceleration amplitude (RMS) at mixing was 150 °C, 0.4 wt. % Al₂O₃ content and 150 °C operating temperature.

REFERENCES

1. Davis D., Shaha A. F., Panigrahib B. B. and Singh S., “Effect of Cr₂AlC nanolamella addition on tribological properties of 5W-30 engine oil”, *Applied Surface Science* 493 1098 - 1105, (2019).
2. Wu B., Song H., Chuan L., Song R., Zhang T., Hu. X., “ Enhanced tribological properties of diesel engine oil with Nano-Lanthanum hydroxide/reduced graphene oxide composites”, *Tribology International* 141, 105951, (2020).
3. Huawei W., Abdullah A., Azeez A. B., Amin S. , Ali K., Pouyan T., “ Curve-fitting on experimental thermal conductivity of motor oil under influence of hybrid Nano additives containing multi-walled carbon nanotubes and zinc oxide”, *Physica A* 535 ,122128, (2019).
4. Umer J., Morris N., Leighton M., Rahmani R., Balakrishnan S., and Rahnejat H., “Nano and microscale contact characteristics of tribofilms derived from fully formulated engine oil”, *Tribology International*, (2018).
5. Mohammad H. E., Ali A. A., and Saeed E., “Improving engine oil lubrication in light-duty vehicles by using of dispersing MWCNT and ZnO nanoparticles in 5W50 as viscosity index improvers (VII)”, *Applied Thermal Engineering* 143 ,493–506, (2018).
6. Sgroi M. F., Asti M., Gili F., Deorsola F.A., Bensaid S., Fino D., Kraft G., Garcia I. and Dassenoy F., “Engine bench and road testing of an engine oil containing MoS₂ particles as nano-additive for friction reduction”, *Tribology International*, (2016).
7. Shubrajit B., Rishabh M., Shubhabrata D. and Pathak S., “Analyses of Anti-wear and Extreme Pressure Properties of Castor Oil with Zinc Oxide Nano Friction Modifiers”, *Applied Surface Science*, 10.1016, (2017).
8. Dinesh R., Giri Prasad M., Rishi Kumar R., Jerome Santharaj N., and Abhishek Raaj A., “Investigation of Tribological and Thermophysical Properties of Engine Oil Containing Nano additives”, *Materials Today: Proceedings* 3 ,45 – 53, (2016).
9. Mohammad H., Masoud A., Davood T., and Hadi R.,” An experimental study on viscosity of alumina-engine oil: Effects of temperature and nanoparticles concentration”, *International Communications in Heat and Mass Transfer*,(2016).
10. Meena L., and Vijay Kumar S.,” Titanium oxide nanoparticles as additives in engine oil”, *Journal of King Saud University – Engineering Sciences*, (2016).
11. Ketan S., Yashvir S., Aadesh R., Virwal H., and Abhishek S.,” Experimental evaluation of the friction and wear of jojoba oil with aluminum oxide (Al₂O₃) nanoparticles as an additive”, *Materials Today: Proceedings*, (2019).
12. Mohsen T., and Arash K., “Improve the thermal conductivity of 10w40-engine oil at various temperature by addition of Al₂O₃/Fe₂O₃ nanoparticles”, *Journal of Molecular Liquids* 283 660–666, (2019).
13. Yuanyuan Z., Yujuan Z., Shengmao Z., Guangbin Y., Chuanping G., Changhua Z., Chunli Z. and Pingyu Z.,” One step synthesis of ZnO nanoparticles from ZDDP and its

tribological properties in steel-aluminum contacts”, *Tribology International* 141 105890, (2020).

13- Rashed A., Nabhan A. “Effects of TiO_2 and SiO_2 Nano Additive to Engine Lubricant Oils on Tribological Properties at Different Temperatures” 20th International Conference on Aerospace, Mechanical, Automotive and Materials Engineering, Rome-Italy, 20 (10) 2463-2472, (2018).

14. Navdeep S., Irfan U., Ankush R., Ankush A., Vinay K. and Sanjay M., “Synthesis and tribological investigation of Al-SiC based nano hybrid composite”, *Alexandria Eng. J.* 57 (3), pp. 1323 – 1330, (2018).

15. Wani K., Ankush R. and Mirirfan U., “Friction and wear characteristics of vegetable oils using for sustainable lubrication”, *Tribol.-Mater., Surf. Interfaces* 12 (1) 27 – 43, (2018).

16. Zhang Z., Simionesie D. and Schaschke C., “Graphite and hybrid nanoparticles as lubricant additives”, *Lubricants* 2 (2) 44 – 65, (2014).

17. Wani K. S., Ankush R., Mir I., “Friction and wear characteristics of vegetable oils using nanoparticles for sustainable lubrication”, *Tribol.-Mater., Surf. Interfaces* 12 (1) 27 – 43, (2018).

18. Zhang Z., Simionesie D., Schaschke C., “Graphite and hybrid nanomaterials as lubricant additives”, *Lubricants* 2 (2) 44 – 65, (2014).